

Activated carbon production from yeast residues to boost up circular bioeconomy

H.R. Modesto¹, S.G. Lemos², J.S. Komatsu³, M. Gonçalves⁴, W.A. Carvalho³, E.N.V.M. Carrilho^{5,*}, G. Labuto^{1,**}

¹Department of Chemistry – Universidade Federal de São Paulo, Diadema - SP, 09913-030 – Brazil

²Department of Chemistry, Universidade Federal da Paraíba, João Pessoa - PB, 58051-970, Brazil.

³Center for Natural and Human Sciences, Universidade Federal do ABC, Santo André - SP, 09210-170, Brazil

⁴Institute of Science and Technology, Universidade Federal de São Paulo, São José dos Campos - SP, 12231-280, Brazil

⁵Department of Natural Sciences, Mathematics and Education, Universidade Federal de São Carlos, Araras - SP, 13604-900, Brazil

Keywords: waste management, waste valorization, physic activation, activated charcoal, chemometric approach

*Presenting author email: elma.carrilho@gmail.com

**Corresponding author: geolabuto@gmail.com

1. Introduction

The exploitation of bio-resources in order to overcome the challenges to be faced will require a process of innovation to boost the global bi-economy. In this sense, it is sought the conversion of biomass, preferably from the management of residues or from renewable sources, in inputs that supply the chemical and pharmaceutical industries, as well as in products for the food industry, for the production of energy and that enable new technological applications, including environmental remediation and green processes (Enriquez-Cabot, 1998; ETP, 2011; Labuto and Carrilho, 2016, Prasad, 2016). In the meantime, a number of activities in the productive sector employ yeasts in fermentative processes generating large amounts of yeast biomasses (YB) as sub products. For example, for each liter of ethanol around 30 g of YB are produced and, considering the projection of the Organization for Economic Cooperation and Development (OECD) that 158 billion liters of ethanol will be produced in 2023, it is possible to evaluate the availability of YB residues. In this way, improving the commercial value of YB, contributing to create new uses for this biomass to insert it in the world bioeconomic market is a pertinent issue. Nowadays, YB has a low prices (around US\$200/ton) and is mainly used as a feed supplement for animals due to its protein content (MAPA, 2015), and after the extraction of β -glucan it becomes a residue (YR). In this way, YR is a renewable, low-cost, and carbon-rich material (ca 43%), requires no comminution, is dried at the end of β -glucan extraction, and is usually discharged in large amounts at accessible locations, which favors the logistic of its transportation (Labuto et al., 2015).

On the other hand, activated carbons (ACs) have a global market of USD 3.22 billion (2018) and it is projected to be higher than USD 6 billions in 2023 (Global and China Activated Carbon Industry Report, 2018-2023). The ACs have an exceptionally high surface area (above 500 m²/g) and well developed internal microporous structure, in addition to the presence of a broad spectrum of functional surface groups (reference). The ACs have gained a prominent global position, being used in food, beverage, fertilizers, pharmaceuticals, automobile, and chemical/metallurgy industries as catalyst and/or as support for catalysts and as adsorbent for different applications (Araujo, 2006). Worldwide, the production of activated carbon depends on mineral carbon or materials of renewable sources, which require a series of steps involving transportation, drying and grinding in the productive process (Ioannidou and Zabaniotou, 2007). This scenario denotes the need of alternatives for the production of high-quality activated carbon from abundant raw material, which associates low cost of production with high yield. Using the principles of circular economy, in the present study YR is used to produce activated carbon by physical activation with CO₂ and water vapor (both also generates in ethanol

production). An experimental design was used to optimize the parameters employed in the activated carbons synthesis and the efficiency of production was monitored by three responses surface area, yield, and percentage of mesopores.

2. Material and Methods

Synthesis and characterization of activated carbon from yeast residue (YR): Known amounts of YR (provided by Biorigin Company, São Paulo – Brazil) were carbonized using a heating program at a 10°C/min temperature rate up 800 °C and remained for 2 h, employing a nitrogen flow (0.1 L/min). An experimental design was conducted for the activated carbons synthesis for which the parameters varied in three levels, activation time (30, 50, and 70 min), CO₂ flow rate (0.09, 0.12, and 0.19, calculated based on residence time of CO₂ inside the reactor), and activation temperature (750, 800, and 850 °C). The responses obtained were yield, surfaces areas, and % of mesopores. Carbonization and activation procedures were conducted in a quartz reactor (45 × 700 mm) in a 1-zone horizontal tubular furnace (FT-1200/H, Fortlab, Brazil). Carbon and CAs produced were characterized by surface area and pore size by gas sorption analysis (BET), X ray diffraction (DRX), elemental analysis, scanning electron microscopy (SEM), Fourier transform infrared spectroscopy (FT-IR), thermogravimetric analysis (TGA), pH at point of zero charge (pH_{PCZ}) and Total Acid Groups (TAG). The best conditions predicted by the experimental design was employed to carry out a new experimental design to evaluate the influence of water vapor and the mixture of CO₂ and water vapor on the physical characteristics of the activated carbon.


3. Results and Discussion E também retirar um pouco do texto aqui

The evaluation of the design was performed considering the three responses yield, surface area, and % of mesopores. The standardized estimated effects (first order and interactions effects) are used in the production of the Pareto charts for the graphical evaluation of the statistical significance of the effects on each response. The obtained model as fitted explains 90.1% of the variability in BET surface area. A lack of fit test was performed. It is designed to determine whether the selected model is adequate to describe the observed data, or whether a more complicated model should be used. Since the p-value for lack-of-fit in the ANOVA table is greater or equal to 0.05, the model appears to be adequate for the observed data at 95.0% confidence level. Only one effect, the first order effect related to activation temperature (p-value < 0.05), indicating that it is significantly different from zero at the 95.0% confidence level. Temperature has a positive effect on surface area and higher surfaces areas can be obtained at 850°C. The Pareto's chart for surface area (Figure 1A) illustrates the statistical significance of this parameter. In this chart, each bar is proportional to the standardized effect presented in decreasing order of importance. The vertical line is used to judge which effects are statistically significant at 95% confidence level. Any bar which extend beyond the line corresponds to the effects which are statistically significant for the biosorption process. As all the effects have positive values, all bars have the same color. Three effects have p-value < 0.05, namely the first order effects related to activation time and activation temperature, and the second order interaction effect between these two factors. These effects have negative signals as one can be denoting in Pareto's chart for yield (Figure 1B). Light and dark gray bars correspond to positive and negative effects, respectively. The ANOVA was performed for the response yield and obtained model as fitted explains 97.0% of the variability in this parameter. A lack of fit test was performed, and the p-value > 0.05, indicating that the model adequately fits the observed data at 95.0% confidence level.

Considering solely the first order effects, higher yields can be obtained at 750 °C and 30 min of activation time. However, the significance of the interaction effect must be considered to understand the combined influence of both factors activation time and activation temperature, in the studied system. In Figure 1C, the behavior of the response yield regarding the AC interaction (activation time vs. activation temperature) points out that there are no significant

differences of yields by performing the activation at 30 min despite the temperature employed, or at 750°C despite the activation time spent. However, yield is significantly lower if the activation is performed at 850°C for 70 min. The desirability function was used to obtain the most adequate activation condition, that is, the one that provides an activated carbon with the highest surface area, yield and percentage of mesopores. The higher desirability was obtained with activation at 850°C, 30 min, and 0.09 L CO₂/min flow rate, corresponding to experiment number 7 of the factorial design, with BET surface area of 511 m²/g, 91.5% of yield, and 11.3% of mesopores.

Figure 1. Pareto's charts for A) surface area and B) yield, and C) Interaction of yield and activation time.

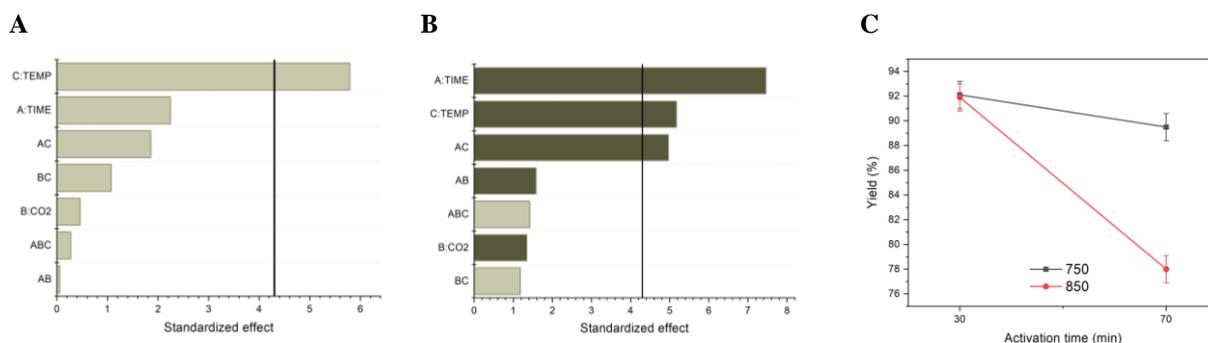

4. Conclusion

It is possible to obtain carbon and activated carbon from yeast residue from fermentative process, employing physical activation, aiming its production in an industrial context of circular economy, allowing the valorization of this type of residue with the possibility of its insertion in the bioeconomic chain.

5. References

- Araujo, P.H.L. Potencial de carvão ativado como suporte catalítico na decomposição de óxido nitroso, 34-35, 2006.
- Enriquez-Cabot, J. Genomics and the World's Economy. *Science Magazine*, 281 (1998) 925-926.
- European Technology Platforms (ETP), 2011. The European bioeconomy in 2030: Delivering Sustainable Growth by addressing the Grand Societal Challenges. Disponível em: <http://www.epsoweb.org/file/560>.
- Ioannidou, O; Zabaniotou, A. Agricultural residues as precursors for activated carbon production—A review, *Renewable and Sustainable Energy Reviews*, 11 (2007) 1966–2005.
- Labuto, G., Carrilho, E.N.V.M, *Bioremediation in Brazil: Challenges to improve the development and application to boost up the bioeconomy*. In: M.N.V. Prasad. (Org.), *Bioremediation and Bioeconomy*, Oxford, 2016, pp. 569-586.
- Labuto, G.; Trama, B.; Castro, G. S.; Guarnieri, B.S.; Silva, F.V.; Colazzo, R. Metals uptake by yeast alive and yeast residue modified by heating process, *Revista Ambiente & Água*, 10 (2015) 510-519.
- MAPA, 2015 Ministério da Agricultura Pecuária e Abastecimento.
- Prasad, M. N. V. *Bioremediation and Bioeconomy*. 1ed., Elsevier. 2016.

Acknowledgements

The authors are grateful to FAPESP financial support (2016/06271-4) and Biorigin Company (São Paulo, Brazil).